

O NOUĂ APLICAȚIE A NANOMATERIALULUI MAGNETITĂ PENTRU ÎNDEPĂRTAREA UNUI SURFACTANT CATIONIC DIN APA UZATĂ

NEW APPLICATION OF MAGNETITE NANOMATERIAL FOR A CATIONIC SURFACTANT REMOVAL FROM WASTEWATER

CRISTINA ILEANA COVALIU¹, IULIANA PĂUN², EUGENIU VASILE^{1,3*}

¹University Politehnica of Bucharest, 313 Splaiul Independenței, 060042, Bucharest, Romania

²INCD ECOIND, 71-73 Drumul Podu Dâmboviței street, 060652, Bucharest, Romania

³National Centre for Micro and Nanomaterials, University Politehnica of Bucharest, 313 Splaiul Independenței, 060042 Bucharest, Romania

The paper presents the adsorption capacity of magnetite nanomaterial for a cationic surfactant removal from wastewater. Kinetic studies were performed by adding the magnetite nanomaterial to a wastewater solution of benzethonium chloride having the concentrations of 2 mg/L and 20 mg/L. The wastewater systems were investigated at 1, 2, 4, 6, 24 and 48 h. The highest removal efficiency (86,98%) was obtained for wastewater containing 2 mg/L benzethonium chloride concentration. The results obtained for the magnetite nanomaterial demonstrates the possibility of applying this nanomaterial for the removal of benzethonium chloride cationic surfactant from wastewater.

Lucrarea prezintă capacitatea de adsorbție a nanomaterialului magnetită pentru îndepărtarea unui agent tensioactiv cationic din apele uzate. Studiile cinetice au fost efectuate prin adăugarea nanomaterialului magnetită într-o soluție de apă uzată care conține clorură de benzetoniu, având concentrații de 2 mg / L și 20 mg / L. Sistemele de ape uzate au fost investigate la intervale de 1, 2, 4, 6, 24 și 48 ore. Cea mai mare eficiență de epurare (86,98%) a fost obținută pentru apele uzate care conțin concentrație de 2 mg/L de clorură de benzetoniu. Rezultatele obținute pentru nanomaterialul magnetită demonstrează posibilitatea aplicării acestui nanomaterial pentru îndepărtarea agentului tensioactiv cationic de clorură de benzetoniu din apele uzate.

Keywords: magnetite nanomaterial, adsorbent, cationic surfactant, wastewater

1. Introduction

An increasing number of products containing cationic surfactants are excessive used worldwide in care products (hair conditioning, cosmetics industry) and in household cleaning products (softening disinfectants, biocides). After utilization, residual amounts of surfactants and their degradation products are discharged into wastewater treatment plants or directly to surface waters and groundwater [1]. The concentration of surfactants in domestic wastewater is between 1 and 10 mg/L [2]. Cationic surfactants were frequently found in water but at lower concentrations. Some of the cationic surfactants such as quaternary ammonium salts belong to the category of emerging pollutants [3]. The presence of these compounds into environment will lead to serious environmental problems including ecological risk and human health damage [4]. In wastewater are found all type of surfactants (anionic surfactants, cationic surfactants, nonionic surfactant and amphoteric surfactants) and their interaction between them may provide an additional complexity to their removal treatment. For these reasons it is important to find the most efficient method of removing surfactants from wastewater. Three methods are used to remove surfactants from wastewaters such as physical methods, chemical

methods and biological methods, but for cationic surfactant removal are recommended to find new and efficient alternative methods. Current research about the removal of surfactants were focused on the optimization of existing biological and chemical wastewater treatment [5]. Only few alternative methods have been studied to remove cationic surfactants from wastewater. Adsorption technologies have been considered most suitable for cationic surfactants removal from wastewater. Removal of cationic surfactants from wastewater using adsorption processes have been studied using a number of adsorbent materials like silica gel [6], bentonites [7], fly ash [8], clays [9], montmorillonite [10], activated carbon [11] and charcoal [12].

New adsorbent nanomaterials such as carbon nanotubes [13], unmodified multi-walled carbon nanotubes [14], zero-valent iron [15], magnetite nanomaterial [16] were investigated for applying within alternative treatment methods for removal cationic surfactants from wastewater. Benzethonium chloride (diisobutylphenoxyethoxyethyl)dimethylbenzylammonium chloride), is an organic cationic surfactant, from the quaternary ammonium salt class, known as Hyamine 1622. Benzethonium chloride is utilized as antimicrobial and antibacterial

* Autor corespondent/Corresponding author,
E-mail: eugeniuvasile@yahoo.com

ingredients in many consumer, industrial and medical products, including eye and nasal drops, soaps, mouthwash, and cosmetics [16]. In composition of medical products, benzethonium chloride is usually found at concentration below 1% [17]. Benzethonium chloride can be found in the food industry where it is used as a surface disinfectant [18]. The methods used for analysis of benzethonium chloride, used as preservative, in Grapefruit Seed Extract [19, 20] are based to HPLC/UV /MS. A HPLC/DAD method for determining anionic (sodium dioctyl sulfosuccinate and sodium 1-dodecane sulfonate), amphoteric (CHAPS (3-[(3-Cholamidopropyl) dimethylammonium]-1-propanesulfonate hydrate)) and cationic (benzethonium chloride) surfactants mixture from surface water has been developed [21]. A spectrophotometric method was developed for the determination of benzethonium chloride in pharmaceutical formulation [22,23].

Although in the scientific literature are found many studies about adsorption materials used for removal from water of other quaternary ammonium salts such as benzalkonium chloride, cetylpyridinium chloride, dodecyltrimethylammonium bromide, hexadecyltrimethylammonium bromide and dodecylamine hydrochloride, the removal of benzethonium chloride from water has been poorly investigated.

In this study magnetite nanomaterial was obtained and tested as new adsorbent for removal of the cationic surfactant, benzethonium chloride, from wastewater.

2. Materials and methods

Benzethonium chloride, Hyamine 1622 (molecular formula: $C_{27}H_{42}ClNO_2$, molecular weight: 448,09 g/mol) was obtained from Sigma-Aldrich. The structure of benzethonium chloride is shown in Figure 1.

The wastewater standard solution had 1000 mg/L of benzethonium chloride.

The magnetite nanomaterial (Fe_3O_4) was synthesized through modified coprecipitation method. Ferric chloride ($FeCl_3 \cdot 6H_2O$), ferrous chloride ($FeCl_2 \cdot 6H_2O$), polyvinylpyrrolidone (PVP), polyethylene glycol 400, sodium hydroxide (NaOH) were supplied from Sigma Aldrich and were used as received.

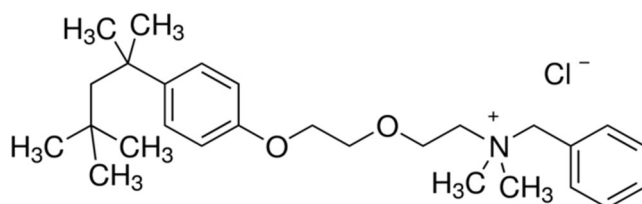


Fig. 1 - Chemical structures of benzethonium chloride. / Structura chimică a clorurii de benzetoniu.

The preparation of magnetite nanomaterial tested in the wastewater process was accomplished using 0.8 mol L⁻¹ aqueous solution of sodium hydroxide and the reaction pH was 12. The molar ratio $Fe^{2+} : Fe^{3+} : PEG : PVP$ unit was 1:2:3:4. The precipitate was separated by centrifugation and washed several times with water. Finally, Fe_3O_4 powder was obtained by precursor calcination at 410°C for 2 h. The X-ray diffraction (XRD) analysis was obtained using a X'PERT PRO MPD with Cu-K α radiation ($\lambda = 0.15418$ nm).

The morphology and crystalline properties of the Fe_3O_4 powder was assessed using a TecnaiTM F30 G² S-TWIN transmission electron microscope with a line-resolution of 1.2 Å and with energy dispersive X-ray (EDAX) spectrometer.

Kinetic studies were performed by adding 0,05 g of magnetite nanomaterial to 500 mL benzethonium chloride wastewater of concentrations 2 mg/L and 20 mg/L. The mixtures were homogenized at 200 rpm for 1, 2, 4, 6, 24 and 48 h. During the experiments, the collected samples were taken for analysis. The concentrations of surfactant were measured by SPECORD 205/ UV-VIS spectrophotometer, at 217 nm wavelength.

The removal efficiency (RE) of the benzethonium chloride from wastewater using magnetite nanomaterials was determined using the following equation:

$$RE\% = 100 \times \left(1 - \frac{C_t}{C_i}\right)$$

where C_t and C_i are the benzethonium chloride t moment and initial.

3. Experimental section

X-ray characterization

The powder obtained from synthesis was analyzed by XRD. The XRD pattern (Fig.2) of oxide

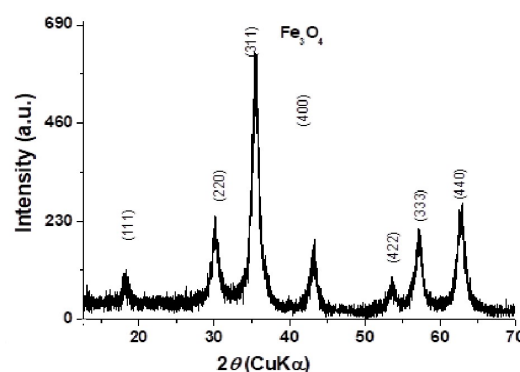


Fig. 2 - XRD patterns of Fe_3O_4 nanomaterial / Difrakția de raze X a nanomaterialului Fe_3O_4 .

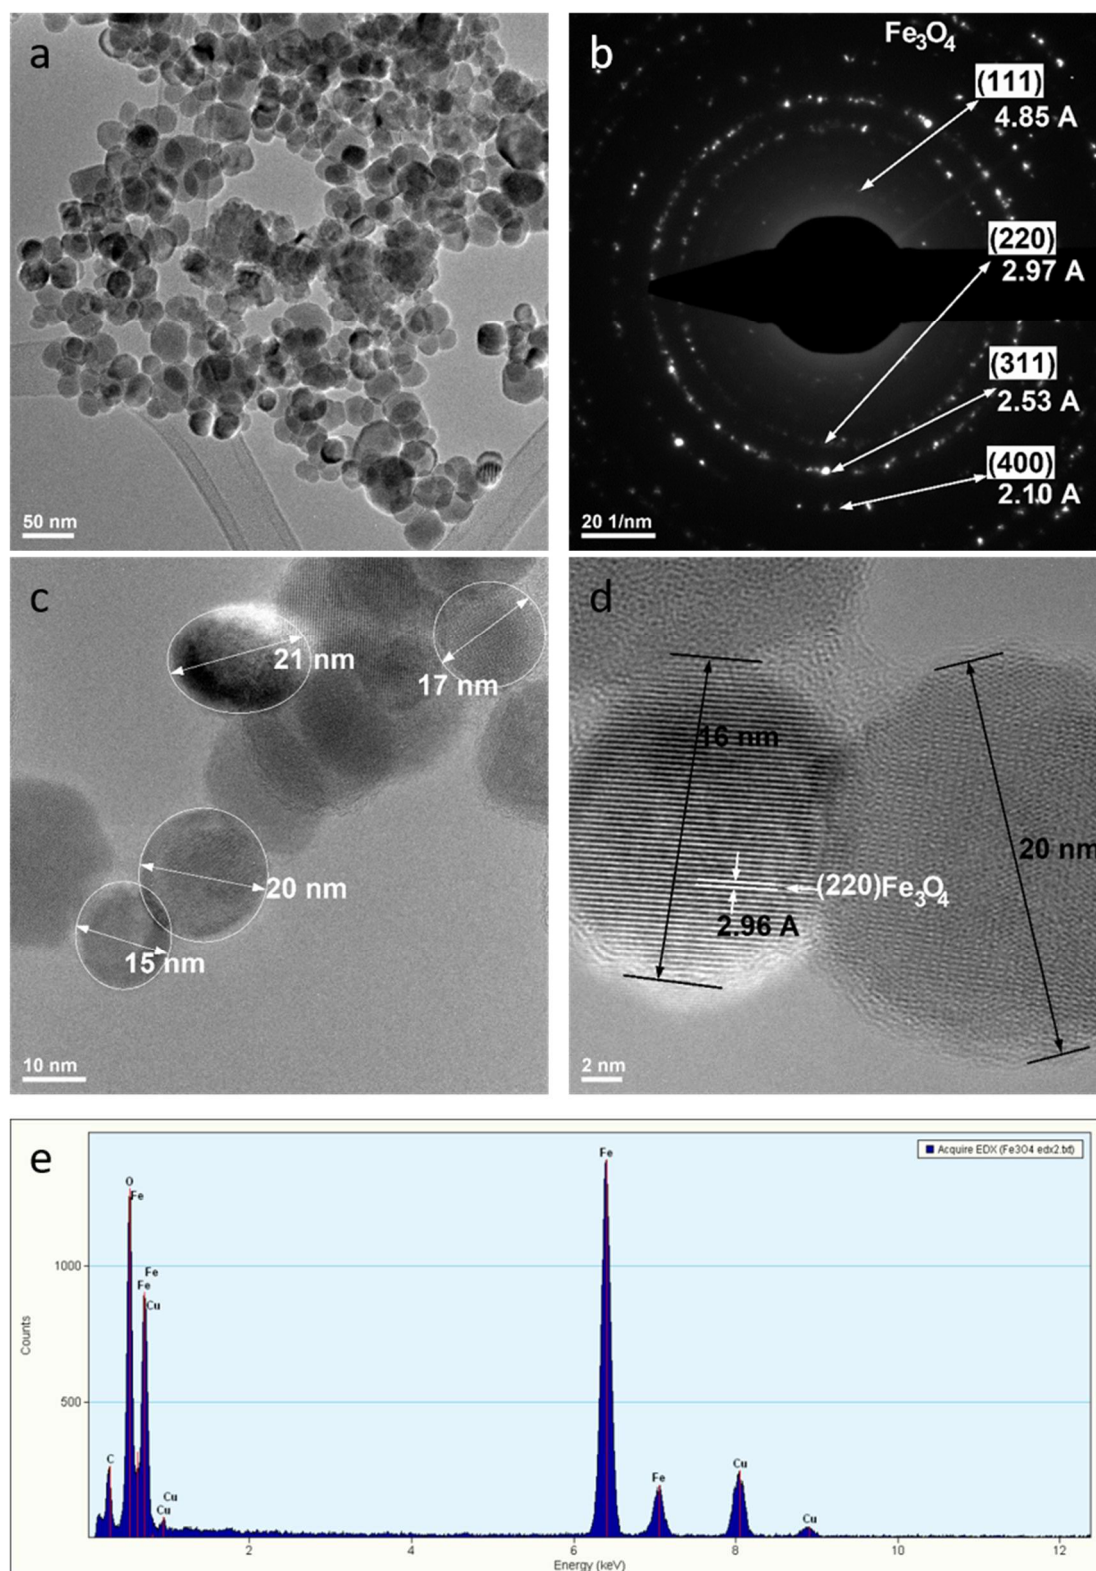


Fig. 3 - TEM of Fe_3O_4 : a) BF-TEM image of Fe_3O_4 nanoparticles agglomeration; b) selected-area electron diffraction (SAED) pattern for the Fe_3O_4 powder associated to the nanoarea in image a; c), d) HR-TEM images; e) EDAX spectrum acquired on the nanoparticles agglomeration from image a. / Rezultate TEM obținute pe nanomaterial Fe_3O_4 : a) Imagine BF-TEM a unei aglomerări de nanoparticule; b) imagine de difracție de electroni (SAED) asociată nanoariei din a); c), d) imagini HR-TEM; e) spectru EDAX achiziționat pe aglomerarea de nanoparticule din a).

powder has proved the formation of single phase compound with inverse spinel structure and cubic symmetry for Fe_3O_4 , in accordance with the

PDF database, ICDD file no. 01-072-8149. The average crystallite size was 15 nm.

TEM analysis

Result of transmission electron microscopy (TEM) investigation are shown in Figure 3.

Figure 3. a), c), d) are TEM micrographs of the Fe_3O_4 nanoparticles. The bright field transmission electron microscopy (BF-TEM) image (Figure 3. a) and high resolution transmission electron microscopy (HR-TEM) image (Figure 3.c) show that the Fe_3O_4 nanoparticles are nearly spherical with diameters between 15 and 25 nm. Nanocrystalline particles with diameter size between 15 and 21 nm are highlighted in Figure 3. c, d. The crystalline structure of the sample was investigated by selected area electron diffraction (SAED) and high resolution transmission electron microscopy (HRTEM). Indexing of SAED image (Figure 3. b) shows that the Fe_3O_4 sample is nanocrystalline (diffraction rings), with a typical face centered cubic (fcc) crystalline structure. The lattice spacing measured on SAED image is in accordance with the standard lattice spacing of Fe_3O_4 from the

PDF database, ICDD file no. 01-072-8149. The parallel fringes existing on HRTEM images (Figure 3. c, d) show the single crystallinity of Fe_3O_4 nanoparticles. In the HRTEM image from Figure 3. d it can be seen the crystalline planes with 2.96 Å interplanar distance corresponding to crystalline family planes with (220) Miller indices of Fe_3O_4 phase.

The chemical composition of the nanoparticles analyzed has been verified by energy dispersive X-ray microanalysis (EDAX). Fe and O are major elements in EDAX spectrum (Figure 3. e) collected on Fe_3O_4 nanoparticles agglomeration from Figure 3.a, confirming the nature of nanoparticles as magnetite. The minor carbon and oxygen elements present in the EDAX spectrum come from the copper TEM grid coated with a thin amorphous carbon film.

Adsorption study

The concentration of benzethonium chloride represented versus time (hours) is presented in Figure 4.

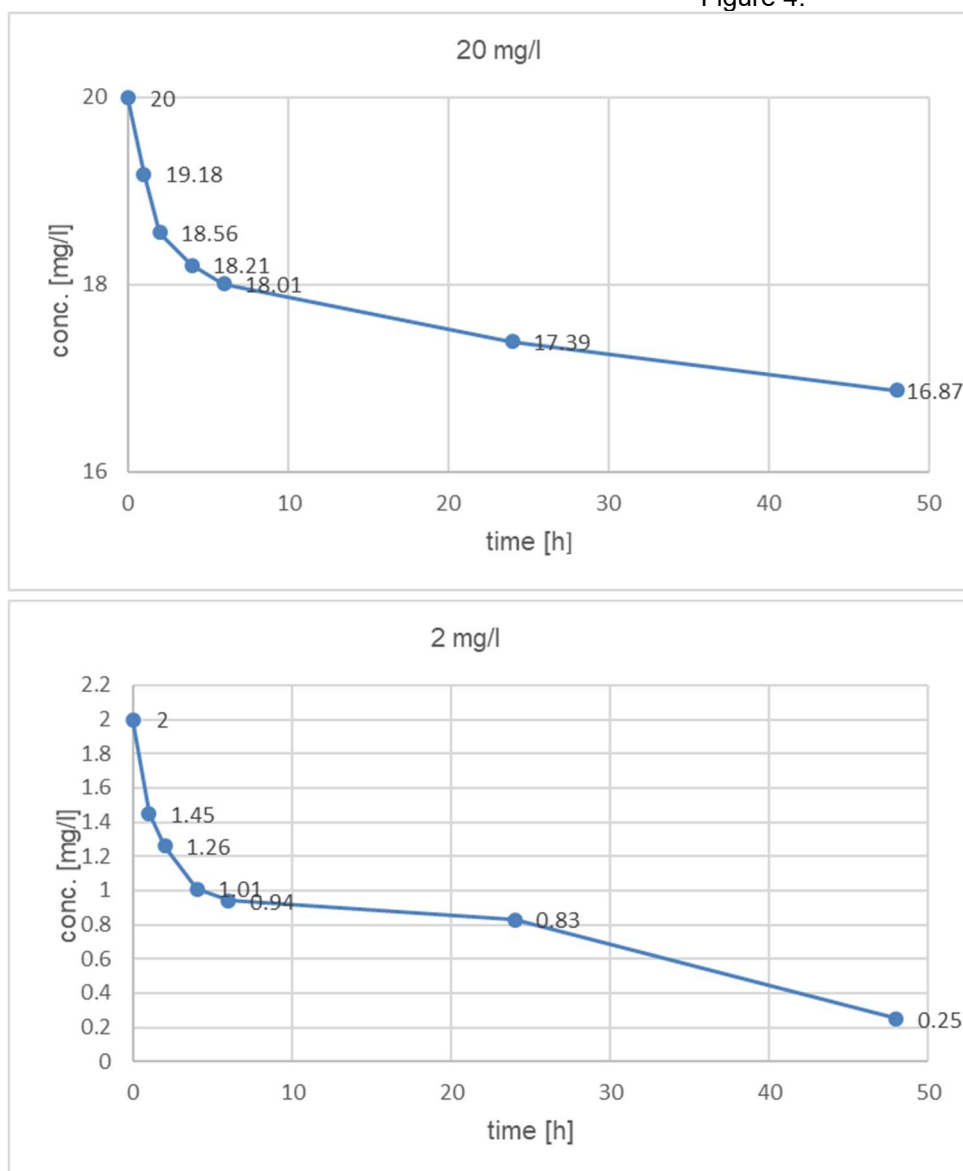


Fig. 4 - Variation of concentration of benzethonium chloride (20 mg/L and 2 mg/L) versus time (h)/ Variația concentrației de clorură de benzetoniu (20 mg/L and 2 mg/L) versus timp (ore).

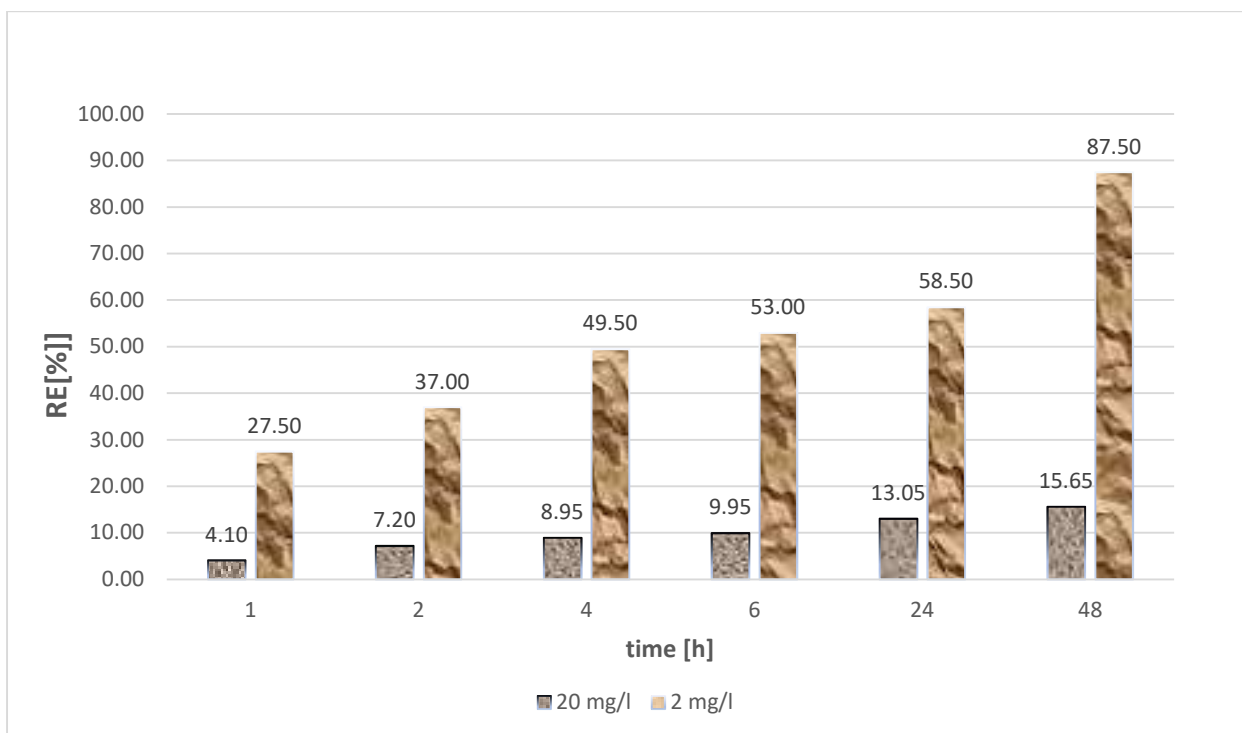


Fig. 5 - The variation of the removal efficiency (RE) % of benzethonium chloride concentration from wastewater versus time (h).
Variația eficienței de îndepărtare (RE) % a clorurii de benzetoniu din apa uzată versus timp (h)

For the wastewater having the concentration of 2 mg /L pollutant the results showed that benzethonium chloride concentration decreased to 0,25 mg /L. The difference of 1,75 mg/L benzethonium chloride represents the absorption capacity of Fe_3O_4 nanomaterial which was about 35 mg benzethonium chloride/ g Fe_3O_4 nanomaterial.

For the wastewater having the concentration of 20 mg/L benzethonium chloride, the results showed that this concentration decreased to 16,87 mg/L, which means that this concentration exceeded the adsorption capacity of Fe_3O_4 nanomaterial. The maximum amount of benzethonium chloride adsorbed on the magnetite nanomaterial was 57 mg/ g nanomaterial.

The variation of the removal efficiency (RE) % of benzethonium chloride concentration from wastewater versus time (h) was presented in Figure 5.

The maximum benzethonium chloride removal efficiency obtained was 87,5 % for wastewater containing 2 mg/L benzethonium chloride and 0,05 mg magnetite nanomaterial, after 48 h of treatment.

4. Conclusions

Increasing number of products containing cationic surfactants excessive used worldwide in care products (hair conditioning, cosmetics industry) and in household cleaning products (softening disinfectants, biocides) leads to the need of finding more efficient ways of wastewater depollution. In this regard, the study that we made was based on

the use of Fe_3O_4 nanomaterial in order to remove benzethonium chloride from wastewater.

Kinetic studies were performed by adding magnetite nanomaterial adsorbent to a wastewater solution of benzethonium chloride having the concentrations of 2 mg/L and 20 mg/L. The wastewater systems were investigated during 1, 2, 4, 6, 24 and 48 h. The highest removal efficiency (86.98%) was obtained for wastewater containing 2 mg/L benzethonium chloride concentration. The results obtained for the magnetite nanomaterial sustains the possibility of applying it for the removal of benzethonium chloride cationic surfactant from wastewater.

Acknowledgment

This work was supported by a grant of the Romanian Ministry of Research and Innovation, CCCDI-UEFISCDI, project number PN-III-P2-2.1-PTE-2019-0628, 39PTE/2020.

REFERENCES

- [1] I. Arslan-Alaton, E. Erdinc, Effect of photochemical treatment on the biocompatibility of a commercial nonionic surfactant used in the textile industry. *Water research*, 2006 **40**, 3409–3418.
- [2] M. I. Bautista-Toledo, J. Rivera-Utrilla, J. D. Méndez-Díaz, M. Sánchez-Polo, F. Carrasco-Marín, Removal of the surfactant sodium dodecylbenzenesulfonate from water by processes based on adsorption/bioadsorption and biodegradation, *Journal of Colloid and Interface Science*, 2014, **418**, 113–119.
- [3] B.O. Clarke, S.R. Smith, Review of 'emerging' organic contaminants in biosolids and assessment of international research priorities for the agricultural use of biosolids. *Environment international*, 2011, **37**, 226–247.
- [4] K. Jardak, P. Drogui, R. Daghrir, Surfactants in aquatic and terrestrial environment: occurrence, behavior, and treatment processes, *Environ Sci Pollut Res*, 2016, **23**, 3195–3216.

- [5] M. Palmer, H. Hatley, The role of surfactants in wastewater treatment: Impact, removal and future techniques: A critical review, *Water Research*, 2018, **147**, 60-72.
- [6] S. Koner, A. Pal, A. Adak, Utilization of silica gel waste for adsorption of cationic surfactant and adsolubilization of organics from textile wastewater: a case study. *Desalination*, 2011, **276**, 142–147.
- [7] R. Zhu, T. Wang, J. Zhu, F. Ge, P. Yuan, H. He, Structural and sorptive characteristics of the cetyltrimethylammonium and polyacrylamide modified bentonite, *Chem. Eng. J.*, 2010, **160**, 220–225.
- [8] S.S. Banerjee, M.V. Joshi, R.V. Jayaram, Effect of quaternary ammonium cations on dye sorption to fly ash from aqueous media. *J. Colloid Interface Sci*, 2006, **303**, 477–483.
- [9] S. Mykola, N. Olga, M. Dmitry, The influence of alkylammonium modified clays on the fungal resistance and biodeterioration of epoxy-clay nanocomposites. *Int. Biodeterior. Biodegrad.* 2016, **110**, 136–140.
- [10] M. Kozak, L. Domka, Adsorption of the quaternary ammonium salts on montmorillonite. *J. Phys. Chem. Solids*, 2004, **65**, 441–445.
- [11] H.D. Choi, J.M. Cho, K. Baek, J.S. Yang, J.Y. Lee, Influence of cationic surfactant on adsorption of Cr (VI) onto activated carbon, *J. Hazard. Mater.*, 2009, **161**, 1565–1568.
- [12] Mahmoud M. Saleh I, Asem A. Atia, Removal of Some Surfactants from Dilute Aqueous Solutions Using Charcoal, *Adsorption Science & Technology* 1999, **17**, 1, 53-63.
- [13] M. Lopez-Lopez, E. Bernal, M.L. Moy, F. Sanchez, P. Lopez-Cornejo, Study of ionic surfactants interactions with carboxylated single-walled carbon nanotubes by using ion-selective electrodes. *Electrochem. Commun.*, 2016, **67**, 31-34.
- [14] M.C. Ncibi, S. Gaspard, M. Sillanpää, As-synthesized multi-walled carbon nanotubes for the removal of ionic and non-ionic surfactants. *J. Hazard. Mater.* 2015, **286**, 195–203.
- [15] H.M. Abd El-Lateef, M.M. Khalaf Ali, M.M., Saleh, Adsorption and removal of cationic and anionic surfactants using zero-valent iron nanoparticles. *J. Mol. Liq.* 2018, **268**, 497–505
- [16] Iuliana Paun, Cristina Ileana Covaliu, Florinela Pirvu, Gigel Paraschiv, Mihai Nita-Lazar Benzalkonium Bromide Cationic Surfactant Removal from Wastewater Using Magnetite Nanomaterial, *Rev. Chim.*, 2020, **71** (4), 289-296
- [17] M. A. Rub, A. Alabbasi, N. Azum, A. M. Asiri, Aggregation and surface phenomena of amitriptyline hydrochloride and cationic benzethonium chloride surfactant mixture in different media, 2020, **300**, 112346
- [18] Final Report on the Safety Assessment of Benzethonium Chloride and Methylbenzethonium Chloride, *Journal of The American College Of Toxicology*, 1985, **4**(5), 65-106
- [19] M. Malmstein, *Surfactants and Polymers in Drug Delivery*, Ed. Swarbrick James, Pharmaceu Tech, Inc. Pinehurst, North Carolina, USA, 2002, 1–26.
- [20] B. Avula, S. Dentali, I. A. Khan, Simultaneous Identification and Quantification by Liquid Chromatography of Benzethonium Chloride, Methyl Paraben and Triclosan in Commercial Products Labeled as Grapefruit Seed Extract, *Pharmazie*. 2007, **62**(8), 593-596
- [21] M. Ganzera, A. Aberham, H. Stuppner, Development and validation of an HPLC/UV/MS method for simultaneous determination of 18 preservatives in grapefruit seed extract, *J. Agric. Food Chem.* 2006, **54**, 3768–3772
- [22] I. Paun, V. I. Iancu, L. Cruceru, M. Niculescu, F. L. Chiriac, Simultaneous Determination of Anionic, Amphoteric and Cationic Surfactants Mixtures in Surface Water, *Rev. Chim.* 2018, **69** (1), 27-30
- [23] Y. M. Issa, H. M. Abdel-Fattah, M. A. S. Allahgi, Spectrophotometric Determination of Benzethonium Chloride Using Some Chromotropic Acid Azo Dyes, *Egypt. J. Chem.* 2019, **62**, Special Issue, Part 1, 267 – 279
